

ICS 25.220.20; 25.220.40

Supersedes
DIN EN ISO 2063-1:2018-02

**Thermal spraying –
Zinc, aluminium and their alloys –
Part 1: Design considerations and quality requirements for corrosion
protection systems (ISO 2063-1:2019);
English version EN ISO 2063-1:2019,
English translation of DIN EN ISO 2063-1:2019-07**

Thermisches Spritzen –
Zink, Aluminium und ihre Legierungen –
Teil 1: Bauteilgestaltung und Qualitätsanforderungen für Korrosionsschutzsysteme
(ISO 2063-1:2019);
Englische Fassung EN ISO 2063-1:2019,
Englische Übersetzung von DIN EN ISO 2063-1:2019-07

Projection thermique –
Zinc, aluminium et alliages de ces métaux –
Partie 1: Considérations de conception et exigences de qualité pour les systèmes de protection
contre la corrosion (ISO 2063-1:2019);
Version anglaise EN ISO 2063-1:2019,
Traduction anglaise de DIN EN ISO 2063-1:2019-07

Document comprises 40 pages

Translation by DIN-Sprachendienst.

In case of doubt, the German-language original shall be considered authoritative.

A comma is used as the decimal marker.

National foreword

This document (EN ISO 2063-1:2019) has been prepared by Technical Committee CEN/TC 240 “Thermal spraying and thermally sprayed coatings” (Secretariat: DIN, Germany) in collaboration with Technical Committee ISO/TC 107 “Metallic and other inorganic coatings”.

The responsible German body involved in its preparation was *DIN-Normenausschuss Schweißen und verwandte Verfahren* (DIN Standards Committee Welding and allied processes), Working Committee NA 092-00-14 AA “Thermal spraying and thermal sprayed coatings (DVS AG V 7)”.

Amendments

This standard differs from DIN EN ISO 2063-1:2018-02 as follows:

- a) references to the informative Annexes E, F and G have been included in the normative part of the standard;
- b) in Table C.1 (Recommended values for the thickness of the metallic coating), the value for the coating material ZnAl15, corrosivity category C4, has been increased from 100 micrometres to 200 micrometres;
- c) the Bibliography has been updated.

Previous editions

DIN 8565: 1962-10, 1966-03, 1977-03

DIN EN 22063: 1994-08

DIN EN ISO 2063: 2005-05

DIN EN ISO 2063-1: 2018-02

The DIN documents corresponding to the international documents referred to in this document are as follows:

| | |
|-----------------------|------------------------------|
| ISO 1463 | DIN EN ISO 1463 |
| ISO 2063-2:2017 | DIN EN ISO 2063-2:2018-02 |
| ISO 2064 | DIN EN ISO 2064 |
| ISO 2178 | DIN EN ISO 2178 |
| ISO 4624 | DIN EN ISO 4624 |
| ISO 8044 | DIN EN ISO 8044 |
| ISO 8501-1 | DIN EN ISO 8501-1 |
| ISO 8501-2 | DIN EN ISO 8501-2 |
| ISO 8501-3 | DIN EN ISO 8501-3 |
| ISO 8502-3 | DIN EN ISO 8502-3 |
| ISO 8503-1 | DIN EN ISO 8503-1 |
| ISO 8503-2 | DIN EN ISO 8503-2 |
| ISO 8503-3 | DIN EN ISO 8503-3 |
| ISO 8503-4 | DIN EN ISO 8503-4 |
| ISO 8503-5 | DIN EN ISO 8503-5 |
| ISO 9223 | DIN EN ISO 9223 |
| ISO 9224 | DIN EN ISO 9224 |
| ISO 9225 | DIN EN ISO 9225 |
| ISO 9226 | DIN EN ISO 9226 |
| ISO 11124-2 | DIN EN ISO 11124-2 |
| ISO 11126-3 | DIN EN ISO 11126-3 |
| ISO 11126-4 | DIN EN ISO 11126-4 |
| ISO 11126-7 | DIN EN ISO 11126-7 |
| ISO 11303 | DIN EN ISO 11303 |
| ISO 12671 | DIN EN ISO 12671 |
| ISO 12679 | DIN EN ISO 12679 |
| ISO 12944-1 | DIN EN ISO 12944-1 |
| ISO 12944-2 | DIN EN ISO 12944-2 |
| ISO 12944-3 | DIN EN ISO 12944-3 |
| ISO 12944-4 | DIN EN ISO 12944-4 |
| ISO 12944-5 | DIN EN ISO 12944-5 |
| ISO 12944-6 | DIN EN ISO 12944-6 |
| ISO 12944-7 | DIN EN ISO 12944-7 |
| ISO 12944-8 | DIN EN ISO 12944-8 |
| ISO 14232-1 | DIN EN ISO 14232-1 |
| ISO 14713-1 | DIN EN ISO 14713-1 |
| ISO 14916 | DIN EN ISO 14916 |
| ISO 14917 | DIN EN ISO 14917 |
| ISO 14918 | DIN EN ISO 14918 |
| ISO 14919 | DIN EN ISO 14919 |
| ISO 14922 (all parts) | DIN EN ISO 14922 (all parts) |
| ISO 14923 | DIN EN ISO 14923 |
| ISO 17834 | DIN EN ISO 17834 |

National Annex NA (informative)

Bibliography

DIN EN ISO 1463, *Metallic and oxide coatings — Measurement of coating thickness — Microscopical method*

DIN EN ISO 2063-2:2018-02, *Thermal spraying — Zinc, aluminium and their alloys — Part 2: Execution of corrosion protection systems (ISO 2063-2:2017)*

DIN EN ISO 2064, *Metallic and other non-organic coatings — Definitions and conventions concerning the measurement of thickness*

DIN EN ISO 2178, *Non-magnetic coatings on magnetic substrates — Measurement of coating thickness — Magnetic method*

DIN EN ISO 4624, *Paints and varnishes — Pull-off test for adhesion*

DIN EN ISO 8044, *Corrosion of metals and alloys — Basic terms and definitions*

DIN EN ISO 8501-1, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 1: Rust grades and preparation grades of uncoated steel substrates and of steel substrates after overall removal of previous coatings*

DIN EN ISO 8501-2, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 2: Preparation grades of previously coated steel substrates after localized removal of previous coatings*

DIN EN ISO 8501-3, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 3: Preparation grades of welds, edges and other areas with surface imperfections*

DIN EN ISO 8502-3, *Preparation of steel substrates before application of paints and related products — Tests for the assessment of surface cleanliness — Part 3: Assessment of dust on steel surfaces prepared for painting (pressure-sensitive tape)*

DIN EN ISO 8503-1, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 1: Specifications and definitions for ISO surface profile comparators for the assessment of abrasive blast-cleaned surfaces*

DIN EN ISO 8503-2, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 2: Method for the grading of surface profile of abrasive blast-cleaned steel — Comparator procedure*

DIN EN ISO 8503-3, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 3: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Focusing microscope procedure*

DIN EN ISO 8503-4, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 4: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Stylus instrument procedure*

DIN EN ISO 8503-5, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 5: Replica tape method for the determination of the surface profile*

DIN EN ISO 9223, *Corrosion of metals and alloys — Corrosivity of atmospheres — Classification, determination and estimation*

DIN EN ISO 9224, *Corrosion of metals and alloys — Corrosivity of atmospheres — Guiding values for the corrosivity categories*

DIN EN ISO 9225, *Corrosion of metals and alloys — Corrosivity of atmospheres — Measurement of environmental parameters affecting corrosivity of atmospheres*

DIN EN ISO 9226, *Corrosion of metals and alloys — Corrosivity of atmospheres — Determination of corrosion rate of standard specimens for the evaluation of corrosivity*

DIN EN ISO 11124-2, *Preparation of steel substrates before application of paints and related products — Specifications for metallic blast-cleaning abrasives — Part 2: Chilled-iron grit*

DIN EN ISO 11126-3, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 3: Copper refinery slag*

DIN EN ISO 11126-4, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 4: Coal furnace slag*

DIN EN ISO 11126-7, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 7: Fused aluminium oxide*

DIN EN ISO 11303, *Corrosion of metals and alloys — Guidelines for selection of protection methods against atmospheric corrosion*

DIN EN ISO 12671, *Thermal spraying — Thermally sprayed coatings — Symbolic representation on drawings*

DIN EN ISO 12679, *Thermal spraying — Recommendations for thermal spraying*

DIN EN ISO 12944-1, *Paints and varnishes — Corrosion protection of steel structures by protective coating systems — Part 1: General introduction*

DIN EN ISO 12944-2, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 2: Classification of environments*

DIN EN ISO 12944-3, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 3: Design considerations*

DIN EN ISO 12944-4, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 4: Types of surface and surface preparation*

DIN EN ISO 12944-5, *Paints and varnishes — Corrosion protection of steel structures by protective coating systems — Part 5: Protective paint systems*

DIN EN ISO 12944-6, *Paints and varnishes — Corrosion protection of steel structures by protective coating systems — Part 6: Laboratory performance test*

DIN EN ISO 12944-7, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 7: Execution and supervision of paint work*

DIN EN ISO 12944-8, *Paints and varnishes — Corrosion protection of steel structures by protective coating systems — Part 8: Development of specifications for new work and maintenance*

DIN EN ISO 14232-1, *Thermal spraying — Powders — Part 1: Characterization and technical supply conditions*

DIN EN ISO 14713-1, *Zinc coatings — Guidelines and recommendations for the protection against corrosion of iron and steel in structures — Part 1: General principles of design and corrosion resistance*

DIN EN ISO 14916, *Thermal spraying — Determination of tensile adhesive strength*

DIN EN ISO 14917, *Thermal spraying — Terminology, classification*

DIN EN ISO 14918, *Thermal spraying — Approval testing of thermal sprayers*

DIN EN ISO 14919, *Thermal spraying — Wires, rods and cords for flame and arc spraying — Classification — Technical supply conditions*

DIN EN ISO 14922 (all parts), *Thermal spraying — Quality requirements of thermally sprayed structures*

DIN EN ISO 14923, *Thermal spraying — Characterization and testing of thermally sprayed coatings*

DIN EN ISO 17834, *Thermal spraying — Coatings for protection against corrosion and oxidation at elevated temperatures*

English Version

Thermal spraying —
Zinc, aluminium and their alloys —
Part 1: Design considerations and quality requirements
for corrosion protection systems
(ISO 2063-1:2019)

Projection thermique —
Zinc, aluminium et alliages de ces métaux —
Partie 1: Considérations de conception et exigences de
qualité pour les systèmes de protection contre la
corrosion
(ISO 2063-1:2019)

Thermisches Spritzen —
Zink, Aluminium und ihre Legierungen —
Teil 1: Bauteilgestaltung und Qualitätsanforderungen
für Korrosionsschutzsysteme
(ISO 2063-1:2019)

This European Standard was approved by CEN on 8 February 2019.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents

| | Page |
|---|------|
| European foreword..... | 4 |
| Foreword | 5 |
| Introduction | 6 |
| 1 Scope | 7 |
| 2 Normative references | 7 |
| 3 Terms and definitions | 8 |
| 4 Criteria for corrosion and corrosion protection by thermal-sprayed coatings | 9 |
| 4.1 General..... | 9 |
| 4.2 Corrosivity categories and environment conditions..... | 9 |
| 4.3 Corrosion rate | 9 |
| 4.4 Coating materials and corrosion behaviour..... | 9 |
| 4.4.1 General..... | 9 |
| 4.4.2 Zinc and zinc alloys..... | 10 |
| 4.4.3 Aluminium and aluminium alloys..... | 10 |
| 5 Requirements for the corrosion protection systems and their planning..... | 10 |
| 5.1 General rules — Technical requirements | 10 |
| 5.2 Used spray materials and coating thickness..... | 11 |
| 5.2.1 Spray materials..... | 11 |
| 5.2.2 Coating thickness | 11 |
| 5.3 Construction design requirements for iron and steel components for thermal spraying | 12 |
| 5.3.1 General..... | 12 |
| 5.3.2 Recommendations for the design of the part — Avoidance of corrosion creating areas..... | 12 |
| 5.3.3 Requirements for welding in combination with thermal-sprayed protective coatings..... | 12 |
| 5.3.4 Thermal spraying of corrosion protected fastenings | 12 |
| 6 Pre-conditions and requirements for the manufacturing process | 12 |
| 6.1 General — Requirements | 12 |
| 6.2 Reference areas | 12 |
| 6.3 Preparation of the surface to be coated | 13 |
| 6.4 Thermal spraying..... | 13 |
| 6.5 Sealing of thermal-sprayed coatings..... | 13 |
| 6.6 Metallic coatings and additional organic top coatings | 14 |
| 6.7 Requirements for the tests — Test procedures | 14 |
| 6.7.1 General..... | 14 |
| 6.7.2 Visual inspection — Appearance..... | 14 |
| 6.7.3 Coating thickness | 14 |
| 6.7.4 Adhesion strength..... | 15 |
| 6.7.5 Metallographic investigation..... | 15 |
| 7 Requirements for the manufacturer..... | 15 |
| 7.1 General..... | 15 |
| 7.2 Coating specification — Requirements for the spray coating..... | 16 |

| | | |
|----------|--|-----------|
| 8 | Documentation | 16 |
| | Annex A (informative) Corrosivity categories — Environment conditions — Exposure | 17 |
| | Annex B (informative) Summary of the corrosion behaviour of thermal-sprayed coatings of zinc, aluminium and their alloys..... | 19 |
| | Annex C (informative) Recommended values for the thickness of the metallic coating | 21 |
| | Annex D (informative) Examples of design and explanations..... | 23 |
| | Annex E (informative) Example test certificate for work specimen for thermal sprayer used on-site in accordance with ISO 2063-2 | 28 |
| | Annex F (informative) Appearance of surfaces in different treated conditions..... | 30 |
| | Annex G (informative) Checklist for this document — Work and test steps and connection to relevant standards or recommendations..... | 31 |
| | Bibliography | 33 |

European foreword

This document (EN ISO 2063-1:2019) has been prepared by Technical Committee ISO/TC 107 “Metallic and other inorganic coatings” in collaboration with Technical Committee CEN/TC 240 “Thermal spraying and thermally sprayed coatings” the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2019, and conflicting national standards shall be withdrawn at the latest by September 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 2063-1:2017.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 2063-1:2019 has been approved by CEN as EN ISO 2063-1:2019 without any modification.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 107, *Metallic and other inorganic coatings*.

This second edition cancels and replaces the first edition (ISO 2063-1:2017), of which it constitutes a minor revision.

The changes compared to the previous edition are as follows:

- Table C.1 has been corrected;
- citations for Annex E, Annex F and Annex G have been added in the text.

A list of all the parts in the ISO 2063 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

In order to protect iron- and steel-based structures (e.g. for steel construction, bridge construction, steel structures for water construction, onshore and offshore wind energy constructions, petrol and natural gas industry) against corrosion, protective coatings are usually deposited. Corresponding to type, shape and required functionality of the part, numerous procedures are available. The deposition of corrosion protection coatings or coating systems can be done by applying hot-dip galvanizing, organic coatings or thermal spraying of zinc, aluminium and their alloys. Using combinations of metallic and organic coatings, duplex corrosion protection coating systems can be produced.

Thermal-sprayed corrosion protection coatings made of zinc, aluminium and their alloys can be sprayed onto all steels which make up the components used in the relevant industrial application. This may be carried out on-site, as well as in the workshop, regardless of the article's size. Due to the usually low heat input into the surface of the part, only a slight thermal loading of the substrate occurs, so that changes in steel properties and deformation of the part do not occur.

Corrosion protection coatings can be used as repairs or rework of defects of other coatings (e.g. uncoated hot-dip zinc galvanized areas) or worn coatings where thermal spraying can be applied on the spot. Due to relative low investment costs, thermal spraying can also be economically applied for single parts.

The ISO 2063 series applies to thermal-sprayed metallic coatings to protect iron and steel against corrosion by deposition of zinc, aluminium or their alloys onto the uncoated surface to be protected.

This document targets designers of components. It covers the planning engineering of the corrosion protection system and deals with the basic rules for planning of corrosion protection systems and for the constructive design of the components to be protected, if the protection system is based upon a thermal-sprayed metallic coating.

ISO 2063-2 targets manufacturers of corrosion protection systems. It deals with the requirements for the execution of the corrosion protection works by thermal spraying in the workshop and on-site.

1 Scope

This document specifies requirements for the protection of iron and steel surfaces against corrosion by applying thermal-sprayed metallic coatings of zinc, aluminium or their alloys.

In this document, requirements for the planning of the corrosion protection system and for the constructive design of the component to be protected are specified, where thermal spraying is intended to be the process for the deposition of the metallic corrosion protection.

Some field-related basic terms are defined and instructions for corrosion behaviour of the zinc and aluminium materials under different environment conditions are provided.

Characteristic properties of the coating, e.g. coating thickness, minimum adhesive strength and surface appearance, are specified and test procedures for thermal-sprayed corrosion protection coatings of zinc, aluminium or their alloys are determined.

This document is valid for applying thermal-sprayed zinc and aluminium protection coatings against corrosion in the temperature range between $-50\text{ }^{\circ}\text{C}$ to $+200\text{ }^{\circ}\text{C}$, taking into consideration the service conditions of any sealants used. Heat-resistant protective coatings of aluminium are covered by ISO 17834 and are not in the scope of this document.

Other corrosion protection processes, e.g. hot-dip galvanizing (galvanic coating), sherardizing, electroplating or selection and deposition of organic coatings/paints are not in the scope of this document.

Requirements for the manufacturing of thermal-sprayed coatings are specified in ISO 2063-2.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1463, *Metallic and oxide coatings — Measurement of coating thickness — Microscopical method*

ISO 2063-2:2017, *Thermal spraying — Zinc, aluminium and their alloys — Part 2: Execution of corrosion protection systems*

ISO 2178, *Non-magnetic coatings on magnetic substrates — Measurement of coating thickness — Magnetic method*

ISO 4624, *Paints and varnishes — Pull-off test for adhesion*

ISO 8044, *Corrosion of metals and alloys — Basic terms and definitions*

ISO 8501-1, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 1: Rust grades and preparation grades of uncoated steel substrates and of steel substrates after overall removal of previous coatings*

ISO 8501-3, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 3: Preparation grades of welds, edges and other areas with surface imperfections*

ISO 12671, *Thermal spraying - Thermally sprayed coatings - Symbolic representation on drawings*

ISO 14232-1, *Thermal spraying — Powders — Part 1: Characterization and technical supply conditions*

ISO 14916, *Thermal spraying — Determination of tensile adhesive strength*

ISO 14917, *Thermal spraying — Terminology, classification*

ISO 14919, *Thermal spraying — Wires, rods and cords for flame and arc spraying — Classification — Technical supply conditions*

ISO 14923, *Thermal spraying — Characterization and testing of thermally sprayed coatings*

EN 10163-2, *Delivery requirements for surface conditions of hot-rolled steel plates, wide flats and sections — Part 2: Plate and wide flats*

EN 10163-3, *Delivery requirements for surface condition of hot-rolled steel plates, wide flats and sections — Part 3: Sections*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14917, ISO 8044 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

service life

expected lifetime of a product (e.g. a structure, component or part) or the acceptable period of use in service

Note 1 to entry: It is also the time that any manufactured item can be expected to be serviceable.

3.2

design life

period of time during which the item (e.g. a structure, component, part or product) is expected by its designers to work within its specified parameters

Note 1 to entry: In the case of series production, it is the period of time between the putting into service of a single item and that item's onset of wearing out.

3.3

life to first maintenance

durability

expected life of a coating system until first maintenance

Note 1 to entry: It is also the time interval that elapses after the initial coating before coating deterioration reaches the point that maintenance is necessary to restore protection of the base metal in accordance with ISO 12944-1.

3.4

protective coating system

sum total of the coats of metal materials and/or paints (duplex coatings) or related products which are to be applied or which have been applied to a substrate to provide corrosion protection in accordance with ISO 12944-1

3.5

pre-fabrication primer

fast-drying paint that is applied to blast-cleaned steel to provide temporary protection during fabrication while still allowing welding and cutting in accordance with ISO 12944-5

Note 1 to entry: In many languages, the term “pre-fabrication primer” does not have the same meaning in English.

3.6

maintenance

sum of all measures to ensure that function of protection of the steel structure against corrosion is maintained

Note 1 to entry: Maintenance includes, but is not limited to, paintwork. Such paintwork can be patch painting (repair included spots/areas of the coating system), patch painting followed by over-painting of the structure or total repairing in accordance with ISO 12944-8.

4 Criteria for corrosion and corrosion protection by thermal-sprayed coatings

4.1 General

Thermal-sprayed coatings of zinc, aluminium and their alloys can significantly increase the effectiveness of the corrosion protection and the service life of the parts. Thermal-sprayed coatings are to be applied preference, if a long time effective corrosion protection is required.

4.2 Corrosivity categories and environment conditions

The corrosivity category provides a basic rule for selecting materials and corrosion protection measures in relation to requirements for the individual application, especially for the service life. Definitions of corrosivity categories and environment conditions are given in ISO 9223 and ISO 12944-2. Additional notes for measuring relevant environment parameters are given in ISO 9225.

Annex A contains a list of typical environments related to the estimation of corrosivity categories.

4.3 Corrosion rate

The corrosion rate of a material is given by the medium and by the exposure time of moisture, air pollution, temperature and contamination of the surface.

ISO 9224 contains information about corrosion rates for different metals. Additional information for metallic materials related to the likelihood of corrosion in the atmosphere environment is given in ISO 9223.

4.4 Coating materials and corrosion behaviour

4.4.1 General

The coating material and the required coating thickness are to be selected and specified in relation to the expected corrosivity, the required design life and construction design.

The corrosion rate of metals and alloys, are not constant over the course of the exposure time. For most metals and alloys, it decreases with time of the exposure due to the accumulation of corrosion products on the surface of the exposed metal.

The corrosion rates of thermal-sprayed coatings are different from bulk materials and other types of metallic coatings due to porosity of thermal-sprayed coatings.

4.4.2 Zinc and zinc alloys

Zinc possesses a high resistance to corrosion due to its passive behaviour against atmospheric attack. However, the corrosion rate per year is affected by the composition of the atmosphere.

The rate of corrosion of zinc or zinc coatings in water depends mainly on the pH value, the carbon dioxide value and the salt and oxygen content of the water. In neutral or slightly alkaline water, zinc corrodes insignificantly only.

Alloying of aluminium up to a content of 15 mass % to the zinc base metal generates a higher corrosion resistance in maritime atmosphere compared to pure zinc metal in the case of lower pH values. It is evidently shown that the passive protection of the aluminium due to its oxidation can be combined with the cathodic protection of zinc.

NOTE Many applications of zinc and zinc alloys in the atmosphere indicate their favourable corrosion behaviour, e.g. the frequent use of thermal-sprayed zinc and zinc alloys for coatings on steel structures in industrial and marine environments and also in form of solid material for roofs and gutters and cast tubes in soils.

Details of the corrosion behaviour of zinc materials (Zn99,99 and ZnAl15) are shown in Annex B.

Further details for zinc, zinc alloys and their corrosion behaviour can be taken from ISO 14713-1.

4.4.3 Aluminium and aluminium alloys

The corrosion behaviour of aluminium materials is characterized by the protection behaviour of the electrical isolating aluminium oxide layer, which is rebuilt spontaneously even after mechanical damage to the surface. Aluminium shows a very high corrosion resistance in slightly acidic to slightly basic media and is particularly suitable for the corrosion protection of steel structures in SO₂-containing industrial atmospheres, as well as in marine environments.

Further details for aluminium, aluminium alloys and their corrosion behaviour in sea water and maritime atmosphere are to be taken from the literature.

A summary of the details for the corrosion behaviour of aluminium materials (Al and AlMg5) are shown in Annex B.

NOTE Aluminium coatings are successfully used in the building industry, where they are applied by electrolytic anodizing or thermal spraying. They have been proven in industrial and marine environments, as well as in seawater immersion.

5 Requirements for the corrosion protection systems and their planning

5.1 General rules — Technical requirements

Application of the thermal-sprayed corrosion protection system requires counter-intuitive design considerations as compared to other coating processes such as hot-dip galvanizing, which are not in the scope of this document. The most adequate corrosion protection system for the specific application should be specified according to the material used and the coating process before starting the design at any time. In the case of a more serious corrosion attack, an additional organic coating should be applied to the spray coating (duplex system), which can increase the corrosion protection significantly.

The following points of view shall be considered and stipulated in a specification, where required.

- a) The corrosion protection system, e.g. a thermal-sprayed coating, sealed and covered by an organic coating, shall be selected in such a way that it complies with the required design life of the component. This is especially valid for surfaces, which are not accessible after assembly. A coating

protection system, which is intended to survive the required design life of the construction with appropriate maintenance, shall be applied.

- b) If there is no protection system available that is likely to survive for the full expected design life, the corrosion protection system shall be planned not to corrode or only corrode insignificantly until the first maintenance is planned. In that way, only the organic coating shall be renewed during maintenance. The adequate period of time to first maintenance shall be stipulated.
- c) Thermal-sprayed metallic corrosion protection coatings may be sealed. The sealant to be used shall be stipulated in the coating specification or the manufacturing instructions. Comparability with further organic coatings and the thermal-sprayed metallic coating shall be considered.
- d) Because thermal spraying can be applied in the workshop, as well as on-site, instructions as to the place of coating application shall be given, if applicable.
- e) If bimetallic corrosion is possible, adequate organic coatings or foils as a barrier are to be stipulated. Organic coating systems can be chosen relative to the corrosivity category in accordance with ISO 12944-5.
- f) ISO 12944-5 provides guidance for the selection of organic coating materials which are also suitable as topcoats for thermally sprayed coatings.

Details for applying the sealing and deposition of the organic coating to a thermal-sprayed coating can be taken from 6.5 and 6.6.

5.2 Used spray materials and coating thickness

5.2.1 Spray materials

Primarily, spray materials of zinc, aluminium or their alloys for applications covered in this document are applied in wire form. In the case of smaller areas and for repairs, spray powders are also used. Usual spray materials are available

- in wire form:
 - Zn99,99 in accordance with ISO 14919, code number 2.1;
 - ZnAl15 in accordance with ISO 14919, code number 2.3;
 - Al99,5 in accordance with ISO 14919, code number 3.2;
 - AlMg5 in accordance with ISO 14919, code number 3.3;
- in powder form:
 - Al 99 in accordance with ISO 14232-1;
 - Zn 99,5 in accordance with ISO 14232-1;
 - ZnAl15 (no standard available).

The spray material to be used shall be specified in the manufacturing instructions.

5.2.2 Coating thickness

Depending upon the service conditions of the construction, the corrosivity of the environment, the requested service life and the expected corrosion resistance of the coating, the composition of the coating and the thickness of the sprayed coating are critical considerations.

In relation to the corrosivity and the selection of the spray material, the minimum coating thickness mentioned in Table C.1 for coatings of zinc, aluminium or their alloys are recommended. The minimum coating thickness shall be specified in the manufacturing instructions.

5.3 Construction design requirements for iron and steel components for thermal spraying

5.3.1 General

The corrosion protection system should be stipulated. This should be the most appropriate for a particular application. The coating should be specified before the design work is started. The design of the part and the specification of the coating should fulfil the instructions of this document and correspond to the recommendations in accordance with ISO 12679.

5.3.2 Recommendations for the design of the part — Avoidance of corrosion creating areas

Components, structures and constructions intended for spray metallizing should be designed considering the general possibilities for operation and limits of the thermal spray processes. The main principles are shown in Table D.1.

Favourable and unfavourable examples of the design for thermal spraying are shown in Figures D.1 to D.4. Further instructions for thermal spraying-related design are provided in Annex D or can be taken from ISO 12679. Further advice for general accessibility can be taken from ISO 12944-3.

5.3.3 Requirements for welding in combination with thermal-sprayed protective coatings

Welding works shall be done prior to thermal spraying. If a construction shall be welded later, the weld zone shall be masked and not be coated up to a distance of about 100 mm from the weld bevel.

If the welding can be applied after thermal spraying, only the area of the weld zone shall be prepared, in accordance with ISO 8501-3, and coated locally. The coating process, e.g. thermal spraying, zinc powder coating, deposition of solder, or an organic coating only, shall be stipulated in the manufacturing instructions.

5.3.4 Thermal spraying of corrosion protected fastenings

The corrosion protection for screws, nuts and other sorts of load-carrying fastenings shall be compatible with the corrosion protection system of the part and should be balanced for the required design life. The current product standards contain specific requirements.

6 Pre-conditions and requirements for the manufacturing process

6.1 General — Requirements

The surface to be corrosion protected by a thermal-sprayed coating shall be unambiguously indicated on the drawing resp. described in the manufacturing instructions. Also, the required minimum thickness and the final conditions of the surface, including the sealing, shall be indicated preferably in accordance with ISO 12671. If further organic coatings shall be deposited, instructions for the organic coating and its application shall be specified in the manufacturing instructions.

NOTE The appearance of the surfaces in different treated conditions (after blasting, thermal spraying, sealing, coated) is shown in Annex F.

6.2 Reference areas

Coated reference areas shall show the durability of the coating system over the service life. Using these guidelines for inspection, the state of the coating shall be evaluated in this area in the presence of an independent supervisor, after a certain or specified service time has elapsed.

In case of spraying very large component surfaces, several reference areas can be required. Location and size of such areas shall be specified by the planning engineering. Selection of the reference area, thermal spraying of the metallic coating and its sealing should be carried out in the workshop,

where the final organic coating can be applied on-site. Application of the entire coating work shall be supervised by an independent test or supervising body. Performance and results of the entire process shall be separately documented.

6.3 Preparation of the surface to be coated

The influence of acceptable surface imperfections (e.g. material depressions, seams, pores, notches) and repairs by grinding or welding for hot-rolled plates, wide flat steel and profiles in accordance with EN 10163-2 and EN 10163-3 shall be considered for surface preparation.

In order to achieve an adequate adhesive strength, the surface shall be pre-treated (degreasing, cleaning and removing of scale and coatings, if present).

For thermal spraying of coatings of zinc, aluminium or their alloys, the surface shall be prepared until the required level of surface cleanliness Sa 2 ½ G for Zn/ZnAl15 and Sa 3 G for Al/AlMg5 is reached. For further details, see ISO 8501-1. ISO 2063-2 contains the requirements for an adequate surface preparation.

A suitable abrasive grit shall be used for blasting prior to thermal spraying; that way, a roughening and enlarging of the substrate's surface will be achieved and the adhesion strength will increase due to mechanical anchoring.

To meet the requirements of the necessary roughness, the coating specification can contain the required surface roughness condition in accordance with ISO 8503-1; that way, the entire coating system shall be considered because by increasing the number of coat layers, the roughness decreases. ISO 2063-2 contains the roughness values usually applied.

6.4 Thermal spraying

Usually, wire flame (WFS) or arc spraying (AS) is applied for thermal spraying of zinc, aluminium and their alloys for corrosion protection. For smaller surfaces and for repairs, powder flame spraying (PFS) is also used. The procedures are described in ISO 14917.

Thermal spraying for corrosion protection covered by this document is usually manually applied; however, it can also be applied mechanically. In order to ensure reproducibility of the coating quality, mechanical or automatic spraying is recommended, where possible.

To ensure adequate quality of thermal spraying, supervision and testing in accordance with ISO 2063-2 shall be stipulated in the manufacturing instructions.

6.5 Sealing of thermal-sprayed coatings

Thermal-sprayed coatings can have a porosity level of up to 15 %, depending on the spray procedure and spray parameter utilized. In order to reduce the internal porosity of the sprayed coating and to close open pores on and near the surface of the sprayed coating, sealants should be applied. In some cases, sealing is used to improve the appearance and the ability to clean the sprayed coating. Sealing reduces the infiltration of dirt and other contaminations into the thermal-sprayed coating (e.g. aggressive salts, other corrosive contaminants).

The sealants applied shall possess a low viscosity to achieve significant penetration. The chosen sealant shall be compatible with the thermal-sprayed coating. Sealants based on alkyd resins should not be applied to zinc and zinc alloys. The compatibility of the sealant with organic coating shall be considered, if applicable.

Sealing should be in accordance with ISO 2063-2.

Natural sealing of thermal-sprayed coatings is also possible and can be achieved by oxidation of the coating, as long as the coating is exposed to an adequate environment and the created oxides, hydroxides and/or basic salts are not soluble under these environmental conditions. However, care shall be taken to avoid rusting before the pores are closed.

6.6 Metallic coatings and additional organic top coatings

ISO 12944-5 gives recommendations for additional organic coatings, which can be applied after sealing of the metallic spray coating, usually called duplex coating system.

ISO 12944-8 and ISO 12944-7 should be considered when planning and applying the organic coating. As long as they are appropriate for the order processing type and handling, organic coatings shall be stipulated in the manufacturing instructions.

6.7 Requirements for the tests — Test procedures

6.7.1 General

Checking the environment conditions (humidity, dew point, temperature of the surrounding and the component) is specified in ISO 2063-2.

Usual tests of the sprayed coatings are:

- non-destructive testing:
 - visual testing;
 - testing of coating thickness;
- destructive testing (test on the accompanying specimen):
 - adhesion testing (pull-off test in accordance with ISO 4624);
 - tensile adhesion testing in accordance with ISO 14916 (for procedure qualification only or, if required, to be specified in the coating specification or manufacturing instructions);
 - metallographic investigations (coating thickness, quality assessment).

Since specific tests cannot be applied non-destructively on the component, accompanying specimens are to be provided. The form of the accompanying specimens shall be suitable to enable destructive testing. Recommendations for the specimen's form are provided in ISO 2063-2:2017, Annex E. The type and number of specimens shall be stipulated in the manufacturing instructions.

The accompanying specimens shall be sprayed using the same spray parameters, which are stipulated in the spray procedure specification (TSPS) for the part. Differences in the spray position (preferably horizontal position, over-head, vertically down), the spray method (manually, mechanically) and the general spray conditions (in the workshop or on-site) shall be considered.

If a test for a specific location of the structure shall be required, a special test piece (e.g. by a mock up) representing the conditions shall be agreed upon between the contracting parties.

6.7.2 Visual inspection — Appearance

The surface of the coating shall be of uniform appearance without inclusions or bare patches and be free from non-adhering particles or defects, which could be detrimental to the service life and expected use of the protective coating. The appearance of surface imperfections and defects is described in ISO 14923. The execution of the visual inspection shall be in accordance with ISO 2063-2.

6.7.3 Coating thickness

Preferably, the coating thickness shall be electromagnetically measured using a mobile coating thickness measuring instrument in accordance with ISO 2178. Location and number of the measuring points are to be chosen such that the measuring results can be adopted as being representative for the entire sprayed coating.

Such coating thickness measuring techniques measure the entire thickness including any sealers and further organic coats. Therefore, the thickness of the metallic layer can only be determined this way before any subsequent layers are applied.

The coating thickness can also be measured destructively on the accompanying specimens (metallographic investigations) (for details, see 6.7.5). This shall be stipulated in the manufacturing instructions, if required.

6.7.4 Adhesion strength

If required, the tensile adhesive strength shall be determined in accordance with ISO 2063-2, following ISO 4624. The mean values of the tensile adhesive strength shall be agreed upon between the contracting parties. Also, if another test procedure is to be applied, its use shall be agreed upon between the contracting parties.

The surface of the component to be coated or the accompanying specimen shall be plane and rigid enough to avoid deflection during testing. In the case of tensile adhesive testing on the component, the position shall be representative for the sprayed coating.

Usually, tensile adhesive testing in accordance with ISO 14916 is not used for quality control measures. If this measurement shall be required, e.g. for qualification matters, the number of accompanying specimens are to be stipulated in the coating specification or manufacturing instructions.

6.7.5 Metallographic investigation

If required, the coating thickness can be determined by metallographic means. A cross-section shall be taken out of a coated accompanying specimen. The investigation shall follow the instructions of ISO 1463.

The main conditions for the assessment of the coating quality are as follows:

- coating defects, e.g. cracks, pores, flaking, peeling, irregular appearance, insufficient coating thickness;
- excessively blasted substrate surface, too many grit residues or pores at the substrate-coating interface;
- oversize single pores or degree of porosity in the coating.

The limiting levels of imperfections to be accepted shall be agreed upon between the contracting parties, if necessary. Test procedure, assessment of the test results and their documentation are specified in ISO 2063-2.

7 Requirements for the manufacturer

7.1 General

Requirements for qualification, manufacturing and testing are specified in ISO 2063-2. To ensure that these requirements will be fulfilled by the applicator, ISO 2063-2 shall be stipulated in the manufacturing instructions of the design engineering, e.g. in a specific manufacturing specification.

If a qualification of the spray procedure specification is required, this shall be stipulated in the manufacturing instructions.

NOTE The work steps and requirements for coating production and testing are based on other relevant standards. For further details, see Annex G.

7.2 Coating specification — Requirements for the spray coating

Due to technical operation demands on the components (e.g. mechanical loading, the corrosive conditions at the service location regarding the corrosivity category), the designer shall draw up a coating specification and define both the coating requirements and the expected service life of the corrosion protection.

That way, the coating specification can also contain requirements for the surface preparation and advices on applying a specific thermal spray procedure.

Usually, the following requirements are to be specified in the coating specification or in the manufacturing instructions for applications covered in this document, if the coating system shall not be selected by the manufacturer of the coating due to contractual agreements and instructions.

- Coating material or spray material.
- Stipulated spray procedure.
- Minimum coating thickness (occasionally, maximum coating thickness also).
- Minimum tensile adhesive strength (MPa) in accordance with ISO 2063-2.
- Surface condition in the as-blasted condition.
- Surface condition in the as-sprayed condition.
- Surface condition in the final machined condition (if applicable).
- Sealing of the sprayed coating, instructions for the sealant.
- Further organic coatings (if applicable).
- Tests and scope of tests.
- Permit of repairs, repair procedures and size of defects or damages due to e.g. transportation, assembly or destructive testing or coating defects.

Details for final condition, storage, transportation, assembly, permit of repairs and testing may also be specified in the manufacturing instructions instead of the coating specification.

Necessary details for the surface preparation for thermal spraying and for the surface conditions prior to spraying can be taken from ISO 2063-2 or they shall be specified in the manufacturing instructions.

8 Documentation

Documentation shall be provided by the manufacturer of the thermal-sprayed coating. It shall contain the tests applied and test results, including those from job reference specimens of the thermal sprayers. Furthermore, designations of the parts, tracing back of the operation steps and quality assurance documents (e.g. work instructions, test instructions and reports, technical data sheets of the blasting grit, the spray material, other coating materials) are to be kept. These requirements are specified in ISO 2063-2.

NOTE Annex E contains an example test certificate for work specimen for thermal sprayer (including spraying procedure and testing). For further details to manufacturing of thermal-sprayed coatings, see ISO 2063-2.

Reports of maintenance and repair works shall be also documented.

Annex A (informative)

Corrosivity categories — Environment conditions — Exposure

Table A.1 — Corrosivity categories — Environment conditions — Exposure

| CC ^a | Typical environment conditions | | Exposure ^b |
|-----------------|---|---|-----------------------|
| | Indoor | Outdoor | |
| C 1 | Not relevant for this document | Dry or cold zone, atmospheric environment with very low pollution and time of wetness, e.g. certain deserts, central Arctic/ Antarctica | VL |
| C 2 | | Temperate zone, atmospheric environment with low pollution (SO ₂ < 5 µg/m ³), e.g. rural areas, small towns. Dry or cold zone, atmospheric environment with short time of wetness, e.g. deserts, sub-arctic areas | L |
| C 3 | | Temperate zone, atmospheric environment with medium pollution (SO ₂ between 5 µg/m ³ to 30 µg/m ³) or some effect of chlorides, e.g. urban areas, coastal areas with low deposition of chlorides, subtropical and tropical zones with atmosphere with low pollution | M |
| C 4 | Spaces with high frequency of condensation and high pollution from production process, e.g. industrial processing plants, swimming pools | Temperate zone, atmospheric environment with high pollution (SO ₂ : 30 µg/m ³ to 90 µg/m ³) or substantial effect of chlorides, e.g. polluted urban areas, industrial areas, coastal areas without spray of salt water, exposure to strong effect of de-icing salts, subtropical and tropical zones with atmosphere with medium pollution | H |
| C 5 | Spaces with very high frequency of condensation and/or with high pollution from production process, e.g. mines, caverns for industrial purposes, unventilated sheds in subtropical and tropical zones | Temperate and subtropical zones, atmospheric environment with very high pollution (SO ₂ : 90 µg/m ³ to 250 µg/m ³) and/or important effect of chlorides, e.g. industrial areas, coastal areas, sheltered positions on coastline | VH |

SOURCE ISO 9223, ISO 12944 (all parts) and ISO 14713-1.

^a CC means corrosivity category.

^b Corrosion exposure time: VL = Very low; L = low; M = Medium; H = high; VH = very high.

Table A.1 (continued)

| CC ^a | Typical environment conditions | | Exposure ^b |
|---|---|---|-----------------------|
| | Indoor | Outdoor | |
| CX | Spaces with almost permanent condensation or extensive periods of exposure to extreme humidity effects and/or with high pollution from production process, e.g. un-ventilated sheds in humid tropical zones with penetration of outdoor pollution including airborne chlorides and corrosion-stimulating particulate matter | Subtropical and tropical zones (very high time of wetness), atmospheric environment with very high pollution (SO ₂ higher than 250 µg/m ³), including accompanying and production pollution and/or strong effect of chlorides, e.g. extreme industrial areas, coastal and offshore areas with occasional contact with salt spray | extreme |
| Im1 | | Fresh water | |
| Im2 | | Sea water in temperature climate | VH |
| Im3 | | Soils | |
| Im4 | | Sea or brackish water | |
| SOURCE ISO 9223, ISO 12944 (all parts) and ISO 14713-1. | | | |
| ^a CC means corrosivity category. | | | |
| ^b Corrosion exposure time: VL = Very low; L = low; M = Medium; H = high; VH = very high. | | | |

Annex B **(informative)**

Summary of the corrosion behaviour of thermal-sprayed coatings of zinc, aluminium and their alloys

Zn99,99

- High corrosion resistance in alkali medium at pH 7 to pH 12.
- Excellent protection against atmospheric corrosion.
- High so-called “cathodic (long-distance protective) reaction”.
- High corrosion resistance in soil with organic coatings.
- Life cycle time proportional to coating thickness.
- Inadequate in the case of higher salt content in air, as for coastal regions.
- Corrosion behaviour similar to that of hot dip galvanizing.

ZnAl15

- Higher corrosion resistance against atmospheric corrosion than zinc.
- Higher corrosion resistance against chlorides and especially SO₂ containing atmospheres than zinc.
- Higher corrosion resistance in soil with organic coatings.
- Inadequate for applying in salt water without organic coating.
- Cathodic protection; however, smaller than for pure zinc.

Al99,5

- High corrosion resistance in media from pH 4 to pH 9.
- Especially sufficient for SO₂ containing industrial atmosphere.
- Well sufficient for marine atmosphere and in seawater.
- High heat resistance.
- Low cathodic protection in the atmosphere.
- Cathodic protection; high only in a strong electrolyte, e.g. sea water.

AlMg5

- As a sprayed coating, it is used in the same places as Al generally.
- As solid material, especially sufficient in marine atmosphere and in sea or brackish water.
- The loss rate in these corrosive media is significantly lower than for pure aluminium.
- Service is also given for environment conditions according to corrosiveness categories Im2 and C5-M (salt water, offshore plants).
- Cathodic protection in the atmosphere is low.

- Cathodic protection; high only in strong electrolytes, e.g. sea water.
- Levels of Mg in sprayed coating can vary between 1,5 % and 4,5 %, depending upon the spray process which shall also be specified, as these variances cause differences in corrosion behaviour.
- AlMg5 spray coatings have a higher hardness than aluminium and aluminium coatings and can be machined and polished easier.

Annex C (informative)

Recommended values for the thickness of the metallic coating

Table C.1 — Recommended values for the thickness of the metallic coating — Life to first maintenance > 20 years

Dimensions in micrometres

| Corrosivity category in accordance with ISO 12944-2 | | Metals — Coating materials | | | | | | | | | | | |
|--|-----------|----------------------------|------|------------------|--------|------|------------------|--------|------|-----------------|-------|------|-----------------|
| | | Zn99,99 | | | ZnAl15 | | | Al99,5 | | | AlMg5 | | |
| | | as | as+s | as+s+oc | as | as+s | as+s+oc | as | as+s | as+s+oc | as | as+s | as+s+oc |
| C1 | very low | 80 | 80 | 50 | 80 | 80 | 50 | NR | NR | — | NR | NR | — |
| C2 | low | 150 | 80 | 50 | 150 | 80 | 50 | 150 | 150 | 150 | 150 | 150 | 150 |
| C3 | medium | 150 | 100 | 80 | 150 | 80 | 80 | 150 | 150 | 150 | 150 | 150 | 150 |
| C4 | high | NR | 150 | 100 ^c | 200 | 100 | 100 ^c | 200 | 200 | 150 | 200 | 200 | 150 |
| C5 | very high | NR | NR | 100 ^c | 200 | 150 | 100 ^c | 250 | 200 | 200 | 250 | 250 | 200 |
| CX | extreme | NR | NR | 200 ^c | 250 | 150 | 100 ^c | 250 | 200 | 200 | 250 | 250 | 200 |
| Im1 | | NR | NR | 100 | NR | NR | 100 | NR | NR | NR | NR | NR | NR |
| Im2 | | NR | NR | 250 ^c | NR | NR | 150 ^c | 350 | 200 | NR ^b | 350 | 200 | NR ^b |
| Im3 | | NR | NR | 100 | NR | NR | 100 | NR | NR | NR | NR | NR | NR |
| Im4 ^a | | NR | NR | 250 | NR | NR | 150 | 350 | 300 | NR | 350 | 300 | NR |
| Key as = as sprayed; s = sealed; oc = organic coating; NR = not recommended ^a In combination with galvanic CP. ^b Overcoating with a thick organic layer is not recommended. However, a thin topcoat or a coloured sealer may be used for decorative purposes. ^c An organic coating suitable for the environment; forms an essential part of this coating system. | | | | | | | | | | | | | |

Annex D **(informative)**

Examples of design and explanations

D.1 Crevices and narrow gaps which arise when back-to-back angles are used, or where stiffeners are welded on by short intermittent filler welds on alternative sides, shall be avoided as they are difficult to protect. Continuous welds are preferred.

D.2 Butt joints should be used in preference to lap joints unless the latter are sealed off by continuous, smoothened welds.

D.3 Corners should preferably be rounded as they are easier to protect than those that are square. They also simplify inspection, cleaning and maintenance and minimize dirt and moisture retention.


D.4 Rounded edges are desirable in order to provide greater surface area to take the protective coating uniformly and to overcome the difficulty of attaining coating thickness on sharp edges. Coatings on sharp edges are also more susceptible to damages.

NOTE Where there are large "edge areas" (e.g. on expanded metal) subject to atmospheric corrosion, it is generally considered to use zinc coating rather than aluminium because zinc gives better cathodic protection to iron and steel.

D.5 Blind crevices, narrow gaps, lap points channels, and horizontal flat surfaces are potential subjects for corrosion attack arising from retention of moisture and dirt including the grit of the surface preparation. If possible an adequate number and location of drainage holes should be available to get rid of moisture by exhausting or run-off.

D.6 Overlapping surfaces to be joined by welding shall be totally sealed by weld seams to prevent entrapment of blasting grit and to prevent the ingress of moisture to not protected areas.


Further examples and figures are presented in ISO 12679.

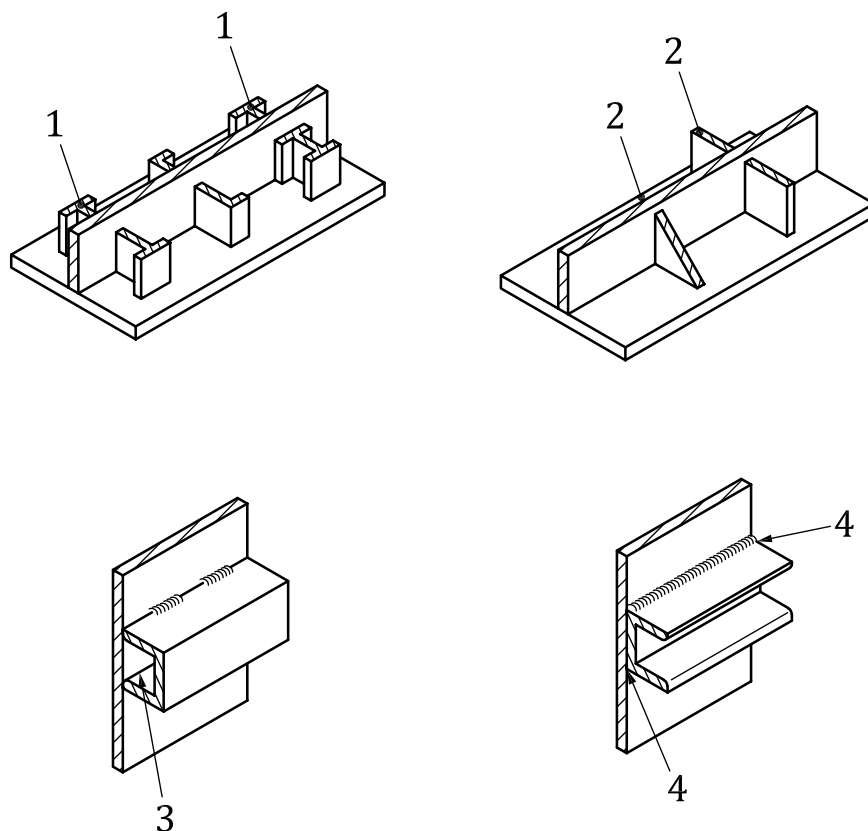

Key

- 1 small section stiffeners or small U beams or channels are to be avoided
- 2 flat steels are to be preferred
- 3 shall be avoided, as far as the interior of the U beam had been corrosion protected prior to welding
- 4 continuous welds, smooth and cleaned of slag and weld spatter are to be preferred


Figure D.1 — Acute interior angles and blind crevices

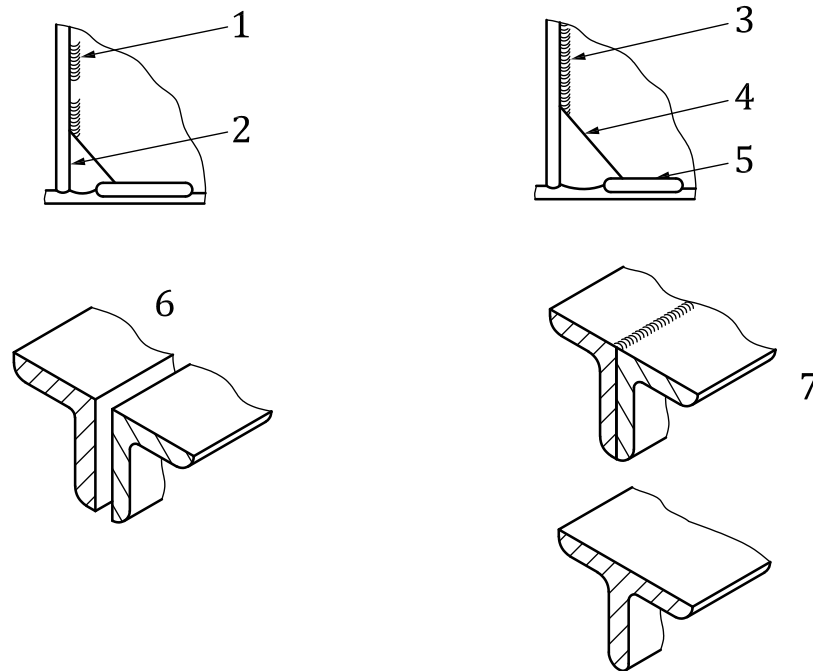

Key

- 1 intermittent stiffener welds are to be avoided
- 2 stiffening plate close to the flange corner shall be avoided because the gap cannot be coated sufficiently
- 3 continuous weld to be preferred
- 4 long snipe to give access is to be preferred
- 5 packing well away from the weld is to be preferred
- 6 back-to-back angles are to be avoided because the gap cannot be coated sufficiently
- 7 continuous welds or similar section T-bars are to be preferred


Figure D.2 — Narrow gaps and crevices

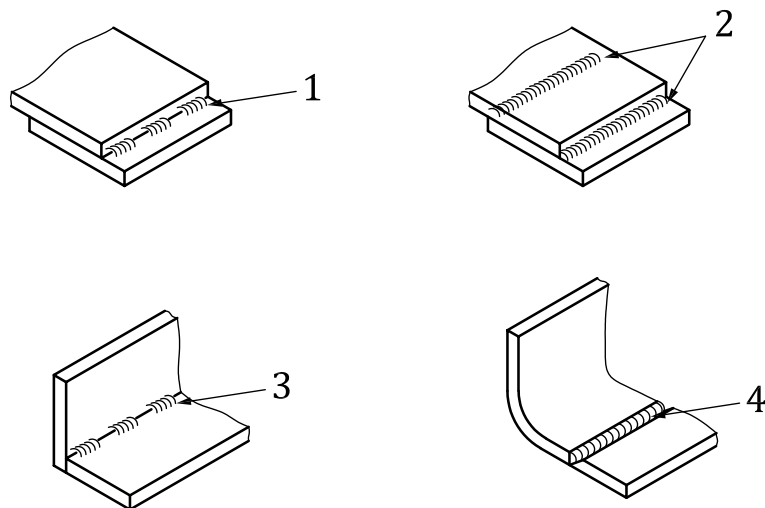

Key

- 1 overlapping joints with discontinuous welds are to be avoided
- 2 overlapping fully sealed by continuous welds, smooth and free from slag and weld spatter are to be preferred
- 3 sharp corners and discontinuous welds are to be avoided
- 4 rounded corners and continuous butt welds are to be preferred

Figure D.3 — Lap joints and corners

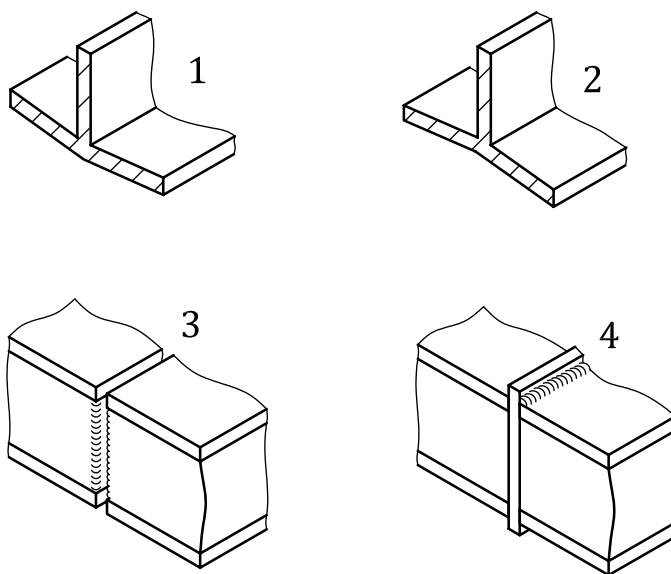

Key

- 1 such design details that dirt and moisture can remain are to be avoided
- 2 pre-bended plate, that water can run-off are to be preferred
- 3 lap joints with discontinuous welds and narrow gaps are to be avoided
- 4 end plate with excess and fully sealed continuous welds is to be preferred

Figure D.4 — Flat surfaces and pockets

Table D.1 — Design considerations for the parts

| Item | To be considered — Solution of problem | To be avoided |
|--|--|---|
| Accessibility | For the surface preparation, cleaning degreasing, grit blasting, testing. | Inaccessible areas |
| | Removal of grit residues. | Deposition of grit residues |
| | For the thermal spraying. | Inaccessible areas |
| | For sealing. | Inaccessible areas |
| | For the deposition of further organic coatings (paints). | Inaccessible areas |
| Possibility to get to | Areas to be coated shall be visible and reachable for the spray jet or tools independent whether the gun or torch is moved manually or by a handling system. | Narrow or not visible areas |
| Available space for motion | Minimum distance of about 300 mm to the surface. (Spray distance, dimension of the spray gun, space for motion of the hose assembly). Spraying can be applied using special deflecting tools. | |
| Spray distance | 100 mm to 300 mm. | |
| Blasting distance | 200 mm to 400 mm (depends on blasting parameter, gun, and nozzle). | |
| Blasting angle | Blasting grit shall approach the surface vertically, if possible. The approach blasting angle shall not be less than 60°. | |
| Spray angle | The spray angle of the spray jet to the surface to be coated should be around 90° and no less than 45°. | |
| Smooth outer contours | Makes the deposition of a corrosion protection system easier to apply. | Recesses, sharp corners |
| Main causes for rust are moisture and dirt | Design of smooth surfaces so that collections of moisture and dirt can be avoided. Supervision, cleaning and maintenance are easier to do. | Residues of moisture and dirt |
| Detail geometries, where water and dirt can collect | See Figures D.1 to D.4. | Narrow gaps, recesses, pockets, channels and horizontal flat surfaces |
| Sharp edges and sharp inner radii | Rounded or chamfered edges and open L, wide U or T profiles are to be applied preferably for reinforcements. | Sharp corners and sharp inner radii |
| Inside located corners and small inner radii | Neither the required surface preparation nor the spraying of the coating can be carried out efficiently. Swirling of the jet when grit-blasting resp. spraying. Use of larger inner radii. | Sharp corners and sharp inner radii |
| Enclosed spaces, e.g. tanks and containers | Manholes for adequate access. A second outlet for adequate ventilation and exhausting of the considerable volume of spray dust and heat. | Unacceptable working conditions, surfaces contaminated by dust |
| Enclosed spaces and hollow parts properly closed | Usually, the inner surfaces will be without corrosion protection. Drainage shall be prepared to take seeped water away, if these hollow parts are not hermetically sealed. | Weathering of not tight enclosed spaces |
| Dividing walls, baffles, crash plates, and fittings, etc. inside tanks and enclosed spaces | They shall be removable. If this is not possible, it shall be decided, whether a reduced quality can be accepted. | Thermal spraying may not be an adequate procedure |

Annex E (informative)

Example test certificate for work specimen for thermal sprayer used on-site in accordance with ISO 2063-2

E.1 Example form

ISO grants the user of this document the right to reproduce or otherwise use this form solely for the purpose of implementing this document.

NOTE JRS means job reference specimen.

| | | | | | |
|--|--|------------------------|--|----------------------|--|
| Name of the thermal sprayer: | | | | Personal No.: | |
| Date of birth: | | Place of birth: | | State: | |
| Employed at: | | | | | |
| Location of company: | | | | | |
| Thermal sprayer, qualified in accordance with ISO 14918: | | | | | |
| Spray procedure: WFS(manually/mechanically sprayed) | | | | | |
| Validity of testing until: | | | | | |

| | | | |
|---|---|----------------|---------------|
| Test standard for work specimen: | ISO 2063-2 | | |
| Test location: on-site: | | | |
| Spray procedure | | | |
| Thermal spray process: | WFS (wire flame spraying) | Method: | Manual |
| Spray procedure specification: | TSPS: | (number) | |
| Test designation: | JRS ISO 2063-2-manual-ISO 14919-2.3 (ZnAl15) | | |

E.2 Tests and test results

| Inspection/Test | Specification | Readings in different positions Direction spray jet/direction motion | | | | Test result | | Inspector |
|---|--------------------------|--|-----|-----|---|-------------|---|-----------|
| | | V/H | H/V | O/H | R | P | F | |
| Visual inspection | ISO 14923 | | | | | | | |
| Coating thickness, μm | ISO 2178 | | | | | | | |
| Roughness test R_z , μm | ISO 8501-1 | | | | | | | |
| Determination of adhesive tensile strength MPa | ISO 4624 / ISO 2063-2 | | | | | | | |
| Positions: V = vertical; H = horizontal; O = overhead; R = radius ($r = 6 \text{ mm}$) Test result: P = passed; F = failed | | | | | | | | |

Work specimen sprayed on (date): on-site:

Work specimen tested on (date): on-site:

Test certificate: valid until:

Date of issue:

Valid for site:

Signatures

Responsible spray supervisor:

Inspector/employment/test body:

.....

.....

(Name in printed letters)

(Name in printed letters)

The licence for spraying is extended to be valid for the site:

Signature

Responsible spray supervisor/coordinator:

.....


(Name in printed letters)

Annex F (informative)

Appearance of surfaces in different treated conditions

Surface treatment process:

- step 1: grit blasting;
- step 2: thermal spraying;
- step 3: sealing;
- step 4: coated (using an organic coating material).

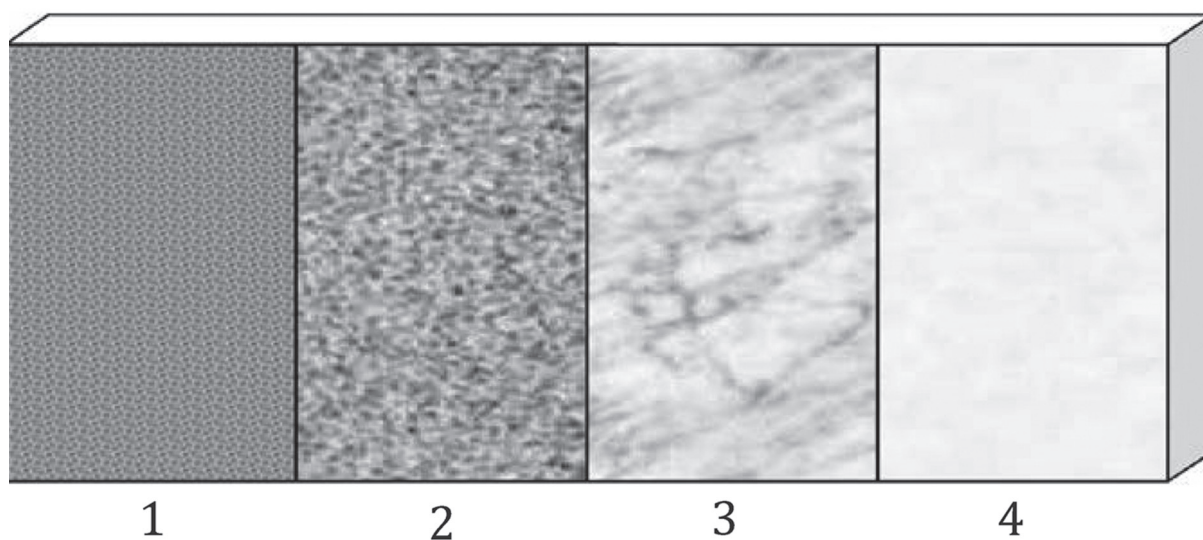

Key

- 1 step 1
- 2 step 1 + 2
- 3 step 1 + 2 + 3
- 4 step 1 + 2 + 3 + 4

Figure F.1 — Appearance of surfaces in different treated conditions

Annex G (informative)

Checklist for this document — Work and test steps and connection to relevant standards or recommendations

Selection shall be done related to the main requirements of the part.

Table G.1 — Checklist

| No. | Activity | Relevant standard | Recommended standards |
|-----|--|--|--|
| 1 | Assessment of the coatability of the component, design considerations considered | ISO 2063-1 | ISO 2063-1 ISO 12679 |
| 2 | Corrosion protection system chosen according to corrosivity category | ISO 2063-1 | ISO 12944-5 ISO 9223 |
| 3 | Corrosion protection system specified in manufacturing instructions resp. on the drawing | ISO 2063-1 | ISO 12671 |
| 4 | Quality requirements specified | ISO 2063-1 | ISO 14922 (all parts) |
| 5 | Quality assurance system required | ISO 2063-1 | ISO 14922 (all parts) (B) |
| 6 | Coating composition defined | ISO 2063-1 | |
| 7 | Minimum coating thickness specified | ISO 2063-1 | |
| 8 | Coating specification established | ISO 2063-1 | |
| 9 | Manufacturing instruction established | ISO 2063-1 | |
| 10 | Required coating defined on the drawing or in the manufacturing instructions | ISO 2063-1 | ISO 12671 |
| 11 | Requirements for preparation of the part to be coated specified (cleaning, degreasing) defined | ISO 2063-1 | ISO 14923 |
| 12 | Instructions for the preparation of the surface to be coated | ISO 2063-1 ISO 8501-1 | EN 13507 |
| 13 | Testing of the blasted surface | ISO 8503-1 ISO 8503-2 ISO 8502-3 | ISO 12944-4 ISO 8503-5 |
| 14 | Spray procedure specification required | ISO 2063-1 | |
| 15 | Component related procedure qualification required | EN 15648 | |
| 16 | Work specimen specified | ISO 2063-1 | ISO 2063-2 |
| 17 | Accompanying specimens, number and form defined and required | ISO 2063-1 | Manufacturing instr. or coating specification. |
| 18 | Instructions for welding work stipulated, preparation and execution on-site | ISO 2063-1 | ISO 2063-2 |
| 19 | Instructions for fastenings stipulated | ISO 2063-1 | |
| 20 | Instructions for sealing of the thermal-sprayed coating stipulated | ISO 2063-1 | ISO 2063-2 |
| 21 | Instructions for organic coating stipulated, if applicable | ISO 12944-5 | ISO 12944-7 |
| 22 | Visual inspection | ISO 2063-1 | ISO 14923 |
| 23 | Measuring the coating thickness | ISO 2178 | |

Table G.1 *(continued)*

| No. | Activity | Relevant standard | Recommended standards |
|-----|---|-------------------------------------|-----------------------|
| 24 | Coating thickness, number of test spots defined and specified | ISO 2063-2 | |
| 25 | Adhesive strength determination | ISO 4624 | ISO 14916 |
| 26 | Metallographic investigation for measuring the coating thickness | ISO 1463 | |
| 27 | Metallographic investigation, if required | ISO 2063-1 manufac. instruct. | ISO 1463, ISO 14923 |
| 28 | Admissible imperfections specified | ISO 2063-1 | ISO 14923 |
| 29 | Documentation with test results and tracing back of the operations required | ISO 2063-1 | ISO 10474 |

Bibliography

- [1] ISO 2064, *Metallic and other inorganic coatings — Definitions and conventions concerning the measurement of thickness*
- [2] ISO 8501-2, *Preparation of steel substrates before application of paints and related products — Visual assessment of surface cleanliness — Part 2: Preparation grades of previously coated steel substrates after localized removal of previous coatings*
- [3] ISO 8502-3, *Preparation of steel substrates before application of paints and related products — Tests for the assessment of surface cleanliness — Part 3: Assessment of dust on steel surfaces prepared for painting (pressure-sensitive tape method)*
- [4] ISO 8503-1, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 1: Specifications and definitions for ISO surface profile comparators for the assessment of abrasive blast-cleaned surfaces*
- [5] ISO 8503-2, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 2: Method for the grading of surface profile of abrasive blast-cleaned steel — Comparator procedure*
- [6] ISO 8503-3, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 3: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Focusing microscope procedure*
- [7] ISO 8503-4, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 4: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Stylus instrument procedure*
- [8] ISO 8503-5, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 5: Replica tape method for the determination of the surface profile*
- [9] ISO 9223, *Corrosion of metals and alloys — Corrosivity of atmospheres — Classification, determination and estimation*
- [10] ISO 9224, *Corrosion of metals and alloys — Corrosivity of atmospheres — Guiding values for the corrosivity categories*
- [11] ISO 9225, *Corrosion of metals and alloys — Corrosivity of atmospheres — Measurement of environmental parameters affecting corrosivity of atmospheres*
- [12] ISO 9226, *Corrosion of metals and alloys — Corrosivity of atmospheres — Determination of corrosion rate of standard specimens for the evaluation of corrosivity*
- [13] ISO 10474, *Steel and steel products — Inspection documents*
- [14] ISO 11303, *Corrosion of metals and alloys — Guidelines for selection of protection methods against atmospheric corrosion*
- [15] ISO 11124-2, *Preparation of steel substrates before application of paints and related products — Specifications for metallic blast-cleaning abrasives — Part 2: Chilled-iron grit*
- [16] ISO 11126-3, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 3: Copper refinery slag*
- [17] ISO 11126-4, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 4: Coal furnace slag*

- [18] ISO 11126-7, *Preparation of steel substrates before application of paints and related products — Specifications for non-metallic blast-cleaning abrasives — Part 7: Fused aluminium oxide*
- [19] ISO 12679, *Thermal spraying — Recommendations for thermal spraying*
- [20] ISO 12944-1, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 1: General introduction*
- [21] ISO 12944-2, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 2: Classification of environments*
- [22] ISO 12944-3, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 3: Design considerations*
- [23] ISO 12944-4, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 4: Types of surface and surface preparation*
- [24] ISO 12944-5, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 5: Protective paint systems*
- [25] ISO 12944-6, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 6: Laboratory performance test methods*
- [26] ISO 12944-7, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 7: Execution and supervision of paint work*
- [27] ISO 12944-8, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Part 8: Development of specifications for new work and maintenance*
- [28] ISO 14713-1, *Zinc coatings — Guidelines and recommendations for the protection against corrosion of iron and steel in structures — Part 1: General principles of design and corrosion resistance*
- [29] ISO 14918, *Thermal spraying — Qualification testing of thermal sprayers*
- [30] ISO 14922 (all parts), *Thermal spraying — Quality requirements of thermally sprayed structures*
- [31] ISO 17834, *Thermal spraying — Coatings for protection against corrosion and oxidation at elevated temperatures*
- [32] ISO 19840, *Paints and varnishes — Corrosion protection of steel structures by protective paint systems — Measurement of, and acceptance criteria for, the thickness of dry films on rough surfaces*
- [33] ASTM D 4541, *Standard Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers*
- [34] DIN 81249-1, *Corrosion of metals in sea water and sea atmosphere — Part 1: Terms and Definitions, basic information*
- [35] EN 582, *Thermal spraying — Determination of tensile adhesive strength*
- [36] EN 657, *Thermal spraying — Terminology, classification*
- [37] EN 13507, *Thermal spraying — Pre-treatment of surfaces of metallic parts and components for thermal spraying*
- [38] EN 15520, *Thermal spraying — Recommendations for constructional design of components with thermally sprayed coatings*
- [39] EN 15648, *Thermal spraying — Component related procedure qualification*